

Monte Carlo Simulations of the Random-Field Ising Model

W. C. Barber and D. P. Belanger

Department of Physics, University of California, Santa Cruz, CA 95064, USA

Ising Monte Carlo simulations of the random-field Ising system $\text{Fe}_{0.80}\text{Zn}_{0.20}\text{F}_2$ are presented for $H = 10$ T. The specific heat critical behavior is consistent with $\alpha \approx 0$ and the staggered magnetization with $\beta \approx 0.25 \pm 0.03$.

It has recently been shown experimentally [1] and through Monte Carlo (MC) simulations [2] that the three dimensional ($d = 3$) dilute, anisotropic antiferromagnet $\text{Fe}_x\text{Zn}_{1-x}\text{F}_2$ in an applied uniform field exhibits the equilibrium critical behavior of the random-field Ising model (RFIM) [3] only for magnetic concentrations $x > 0.75$. Although there is some agreement between previous MC and equilibrium experimental data, particularly the staggered susceptibility critical exponent, where $\gamma = 1.7 \pm 0.2$ for MC [4] and $\gamma = 1.58 \pm 0.08$ for experiment [1], and the correlation length critical exponent, where $\nu = 1.1 \pm 0.2$ for MC [4] and $\nu = 0.88 \pm 0.05$ for experiment [1], the experimental value [5] of the specific heat exponent, $\alpha = 0.00 \pm 0.02$, disagrees substantially with the simulation result [4] $\alpha = -0.5 \pm 0.2$. The order parameter exponent, $\beta = 0.00 \pm 0.05$ from simulations [4], has yet to be measured experimentally. The MC exponents violate the Rushbrooke scaling inequality $2\beta + \gamma + \alpha \geq 2$, indicating possible inconsistencies. The previous MC studies employed finite scaling on ferromagnetic lattices of sizes $L \times L \times L$, with $L \leq 16$. Simulations were made over many random-field configurations and equilibrium was ensured by insisting that different starting configurations yielded consistent results at each temperature. In the present MC study, we have explored a much larger antiferromagnetic lattice and modeled our simulations closely after $\text{Fe}_{1-x}\text{Zn}_x\text{F}_2$ and the thermal cycling procedures used in experiments. Our large lattice size prevented the averaging over many random-field configurations, though the results obtained for a few different configurations yielded consistent results. We determined the staggered magnetization, M_s , and C_m versus T . The resulting C_m more closely mimics the symmetric, nearly logarithmic C_m peak of the experiments [5] than the nondivergent cusp found in the earlier MC studies. In addition, we find $\beta = 0.25 \pm 0.03$, in disagreement with the previous MC studies.

The body-centered-tetragonal magnetic lattice of $\text{Fe}_{0.80}\text{Zn}_{0.20}\text{F}_2$ is modeled as two cubic sublattices delineated as one-dimensional arrays bit coded to allow for a very large lattice size, $2L \times L \times L$ with $L = 128$, corresponding to 3.4×10^6 spins. Periodic boundary conditions are imposed. The dilute MC Ising Hamiltonian is

$$H = J_2 \sum_{\langle ij \rangle} \epsilon_i \epsilon_j S_i S_j - h \sum_i \epsilon_i S_i \quad (1)$$

where $S_i = \pm 2$ and $\epsilon_i = 1$ if site i is occupied and zero if not, $J_2 = 3.17$ K and $h = 8.73$ K. This approximates the experimental system which has one dominant Heisenberg exchange interaction, J_2 , and a large single-ion anisotropy. The very small, frustrating interactions, J_1 and J_3 , are not included. The MC value for J_2 is 0.60 times that of FeF_2 so that $T_c(0)$ corresponds roughly to that of the experimental system. The value of h is chosen to have roughly the same effect as a field $H = 10$ T in the real system, as determined by the fields at which low temperature spin flips occur. This field also yields a shift $T_c(0) - T_c(H)$ consistent with $H = 10$ T in the real system [6]. Henceforth we refer to the applied uniform field as $H = 10$ T.

For $H = 0$, the sample is cooled to low temperatures in steps of 0.01 K while magnetic sites are randomly visited an average of N times, where $2000 < N < 5000$, and flipped with a probability given by the metropolis algorithm. Similarly, the sample is heated from an ordered state to above the transition. No hysteresis is observed at $H = 0$ using these two procedures. For $H > 0$, two thermal cycling procedures are used to mimic those of the experiments. Each site is visited $5000 < N < 10000$ times per 0.01 K temperature step. For zero-field cooling (ZFC), the sample is

started at $H = 0$ in a well ordered state (in experiments this state is prepared by cooling in $H = 0$), the field is subsequently applied, and the sample is heated through $T_c(H)$. In field-cooling (FC), the sample is cooled with H applied. We observe no significant hysteresis with these two procedures, consistent with the experiments. M_s and C_m are calculated for each temperature. The simulations are performed on Linux/Gnu computers with CPU speeds between 350 to 450 MHz. Individual runs with $L = 128$ at 5000 MC steps per spin and covering 10K in T typically take one week of CPU time. We have not seen any significant dependence on N in the range studied.

Figure 1 shows C_m versus T for $L = 128$ and $N = 5000$ for $H = 0$ and for ZFC and FC at $H = 10$ T. Each point represents a point-by-point derivative of the energy which is itself averaged over 0.1 K intervals. The behavior is very similar to that observed in birefringence and pulsed heat experiments [5]. Namely, the $H = 0$ behavior exhibits the asymmetric cusp ($\alpha < 0$) characteristic of the random-exchange Ising model and, for $H > 0$, a much more symmetric peak near $T_c(H)$ consistent with the symmetric, nearly logarithmic divergence. Previous MC studies employing finite size scaling did not yield this behavior.

Figure 2 shows the ZFC M_s versus $T - T_c$ for $L = 128$ and $N = 5000$ for $H = 0$ and $H = 10$ T. Fits of the data for various ranges of $|t|$ within $10^{-3} < |t| < 10^{-1}$, yield the critical order-parameter exponent $\beta = 0.35 \pm 0.04$ for $H = 0$ (REIM) and $\beta = 0.25 \pm 0.03$ at $H = 10$ T (RFIM). The $T_c(H)$ values used in the fits were constrained by the fits to $C_m(H)$.

To demonstrate that the results of the simulations are close to equilibrium, we did a simulation just below the transition for $L = 128$, $H = 10$ T, and $T = 60.5$. One lattice was started fully ordered, another fully ordered but with the sublattices reversed, and one randomly ordered. All three lattices converged to the same energy and M_s within expected fluctuations after 5000 steps per spin.

Using $\beta = 0.25 \pm 0.03$ from MC and $\alpha = 0.02 \pm 0.02$ and $\gamma = 1.58 \pm 0.08$ from experiments, we obtain $2\beta + \gamma + \alpha = 2.08 \pm 0.14$, which is consistent with the Rushbrooke scaling relation as an equality. Further studies will be needed to understand why the MC simulations with large antiferromagnetic lattices and thermal cycling yield different results than the earlier ferromagnetic MC simulations with finite scaling analyses [4]. For simulations of RFIM critical behavior employing dilute antiferromagnets, the magnetic concentration should be kept well above the percolation threshold concentration for vacancies.

This work has been supported by the Department of Energy Grant No. DE-FG03-87ER45324.

-
- [1] Z. Slanić, D. P. Belanger and J. A. Fernandez-Baca, Phys. Rev. Lett. 82 (1999) 426.
 - [2] W. C. Barber and D. P. Belanger, J. Appl. Phys. 87 (2000) 7049.
 - [3] D. P. Belanger, "Spin Glasses and Random Fields", ed. A. P. Young World Scientific (1998) 251.
 - [4] H. Rieger, Phys. Rev. B 52 (1995) 6659; H. Reiger and A. P. Young, J. Phys. A 26 (1993) 5279.
 - [5] Z. Slanić and D. P. Belanger, J. Magn. Magn. Mater. 186 (1998) 65.
 - [6] I. B. Ferreira, A. R. King and V. Jaccarino, Phys. Rev. B 43 (1991) 10797.

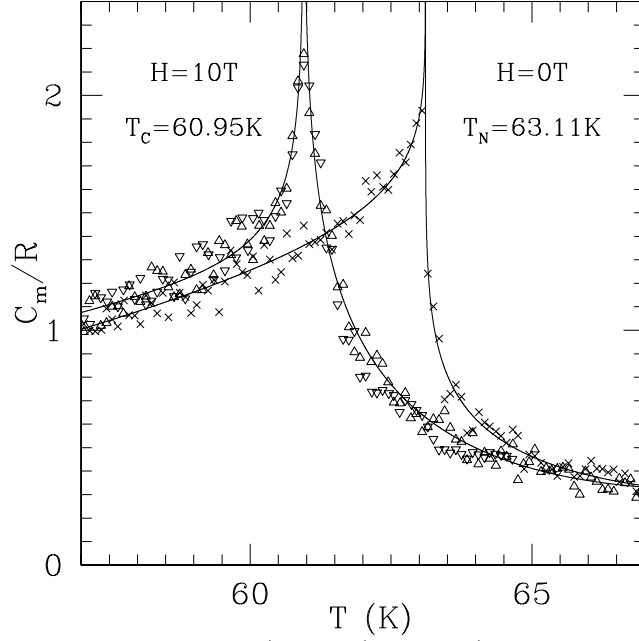


FIG. 1. C_m vs. T for $H = 0$ and for ZFC (triangles) and FC (inverted triangles) at 10 T with $L = 128$ and $x = 0.80$. Note the symmetric peak for $H = 10$ T. The curves are fits to the data with $\alpha = -0.09$ and 0.00 for the $H = 0$ and $H = 10T$ cases, respectively.

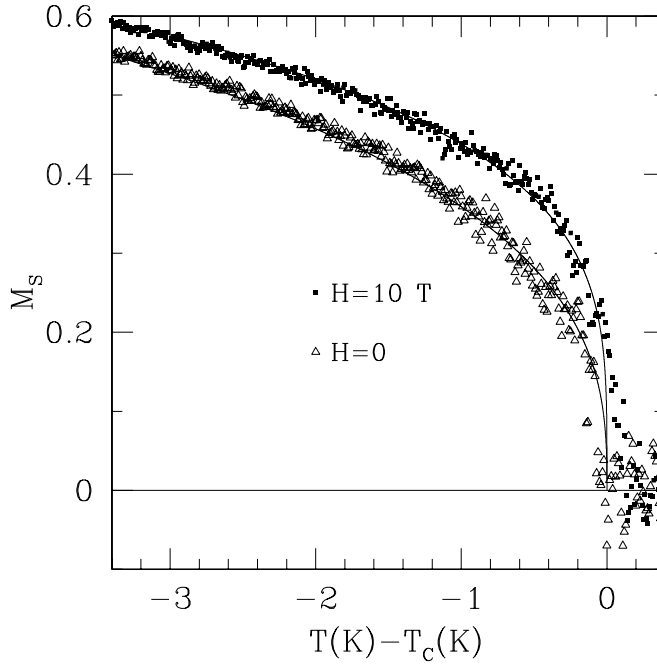


FIG. 2. M_s vs. $T - T_c$ for $H = 0$ and ZFC at $H = 10$ T with $L = 128$ and $x = 0.80$. The curves are fits to the data with $\beta = 0.35$ and 0.25 for the $H = 0$ and $H = 10T$ cases, respectively.